

Optical Frequency Response of GaN-based Light-emitting Diodes with Embedded Photonic Crystals

Yu-Feng Yin, Yen-Hsiang Hsu, Liang-Yu Su, Yuan-Fu Hsu, Li-Cheng Chang,
Chao-Hsin Wu, and JianJang Huang

Graduate Institute of Photonics and Optoelectronics, National Taiwan University,
No. 1, Roosevelt Road, Taipei, 10617 Taiwan
Phone: (886)-2-3366-3665 EMAIL: f99941063@ntu.edu.tw, jjhuang@ntu.edu.tw

Keywords: LED, GaN, photonic crystal, sub-GHz

Abstract

In this study, sub-GHz modulation of GaN-based photonic crystal light-emitting diodes (PhCLEDs) were demonstrated. The higher operation speed is attributed to faster radiative carrier recombination of extracted guided modes from the PhC microcavity. The optical -3-dB bandwidth up to 240 MHz (an 1.5-fold increase as compared to a conventional LED) is achieved.

INTRODUCTION

In the past few decades, the speed of heterogeneous wireless access network (WAN) has grown rapidly since the effort done and progress in electro-optical (EO) devices and circuit designs. For low-data-rate applications especially, such as home security/automation, sub-GHz radios offer relatively simple wireless solutions that can operate uninterruptedly with longer range, reduced power consumption, and lower operating cost [1]. In an indoor wireless communication, visible light communication (VLC) offers another sub-GHz wireless embodiment due to the replacement of incandescent bulbs with high-efficiency Light-emitting Diodes (LEDs) in general illumination [2]. With the continuing advances in III-V alloy system, GaN-based LEDs as VLC sources possess several advantages including stability of the optical output power, resistance to wavelength shift, and good carrier confinement [3]. To this end, both green and blue LEDs have been demonstrated with the optical bandwidth up to 330 MHz and 225.4 MHz [2, 4]. For the photonic crystals (PhCs) embedded light-emitting devices, they exploit not only the photonic band selection but also higher modal quality factor (Q -factor) in the PhC region [5]. Therefore, to achieve a higher optical output, PhCs is often employed in high efficiency photonic components such as LEDs and Lasers. For instance, PhC LEDs (PhCLEDs) exhibits a narrower linewidth, higher output power and better directionality owing to its microcavity structure [5]. A lower-order mode extraction and enhanced Purcell factor also have been characterized and demonstrated in our previous work [6].

In this study, we employ PhCs as an active out-coupler in an effort to allow Bragg scattering and prevent light

trapping in the device. With a reduced radiative carrier lifetime and intense photon accumulation in some photonic bands, a higher optical output power and larger modulation bandwidth are obtained in the radio frequency (RF) response analysis.

DEVICE FABRICATION

The detailed epi-structures and process flows of the devices were described elsewhere [5]. To increase the interaction between guided modes and PhCs, the PhC nanohole array was fabricated within the light-emitting area with a depth of 700 nm and a transparent conducting layer (TCL) on top of it. For the frequency response characterization, a GSG (ground-signal-ground) RF contact pad were deposited on Benzocyclobutene (BCB) planarization polymer. PhC nanohole arrays were hexagonally arranged with a lattice constant (A) = 500 nm, and an aspect ratio which was radius (R)/ A =0.35 as shown in Fig. 1(a). The light-emitting area is defined by the TCL in a rectangular shape with a width of 60 μm and four kinds of length of L (54, 100, 200, and 400 μm). Figure 1(b) shows the detailed layout of the device with a 3- μm -wide line microcavity formed within the PhC region and the left inset is the optical microscope (OM) image of the device with $L = 54 \mu\text{m}$. PhCLED were named according to the TCL length as PhC54, PhC100, PhC200 and PhC400 respectively. Conventional planar LED (CLED) without PhC region were also fabricated and named as C54, C100, C200, and C400. Figure 1(c) depicts the cross-section view of a PhCLED structure with 700-nm-deep PhCs.

EXPERIMENTAL RESULTS AND DISCUSSIONS

Figure 2 shows L-I and I-V curve of the design PhCLEDs, where the turn-on voltages are between 4 V ~ 4.5 V with a leakage current on the order of nA at a -5 V bias condition. The I-V characteristics indicate that the PhCs etched deeply through the active layer don't deteriorate the electrical property much. PhC400 presents a lower resistance and the highest optical output with a 17% enhancement over C400. The spontaneous optical frequency responses for four different layouts under an injection current 50 mA are shown in Fig.3. The highest $f_{3\text{dB}}$ bandwidth of 240 MHz is obtained from PhC54.

Although the resistance of a smaller mesa slightly increases, the capacitance of the PhC54 is reduced to one fifth of the one of PhC400. Figure 4 concludes the relation of the obtained bandwidth of PhCLEDs at a various injection condition. It can be seen that the bandwidth of PhCLEDs increase approximately as $(J)^{0.28}$ which is slower than the ones of CLEDs according to the relation of the power bandwidth product and the injection carrier density [7]. However, PhCLEDs show a better high-speed performance than CLEDs. Also, a 50% bandwidth enhancement is obtained in the PhCLEDs as compared to the result of a CLEDs. A planar LED may have an even smaller capacitance with a $54 \times 3 \mu\text{m}^2$ light-emitting area, but the current density around the line microcavity is so high that would degrade the device performance. For PhCLEDs, the PhC regions not only mitigate the current crowding in the small light-emitting area but provides a better photon confinement by the PhCs. Therefore, the shortened photon lifetime in a PhC-embedded LED pushes the modulation toward higher speed under the same injection current density.

CONCLUSIONS

In summary, we report a 50% high-speed performance improvement of GaN-based LED by using a photonic crystals embedded structure in the light-emitting area. The PhCs not offer only a better light extraction but reduce the possibility of device degradation in a small light-emitting area. The proposed PhCLED structure enables a stable operation of a small LED with a smaller device capacitance, higher photon accumulation on specific photonic bands, and a shorter photon lifetime, leading to a larger modulation bandwidth.

ACKNOWLEDGEMENTS

This work was supported by the Ministry of Science

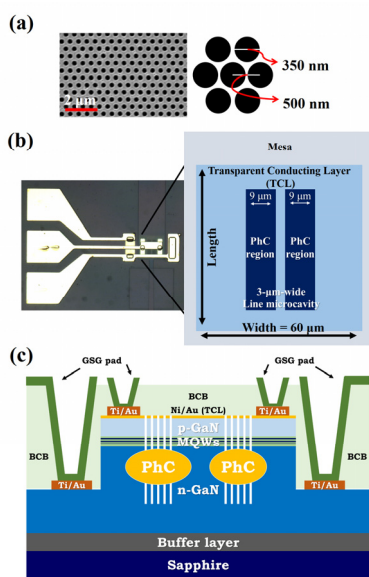


Fig. 1 (a) SEM of the design PhCs (b) Layout of the light-emitting area and PhC region. Left inset is the OM image of PhC54. (c) Cross-section structure of PhCLED.

and Technology under the grants MOST 103-2218-E-002-002

REFERENCES

- [1] De Nardis, *et al.*, "Overview of the IEEE 802.15.4/4a standards for low data rate wireless personal data networks," Positioning, Navigation and Communication, 2007. WPNC '07. 4th Workshop on, pp. 285-289, 22-22 Mar. 2007.
- [2] McKendry, *et al.*, "High-speed visible light communications using individual pixels in a micro light-emitting diode array," Photon. Technol. Lett., IEEE, vol. 22, no. 18, pp.1346-1348, Sep. 2010.
- [3] R. Wirth, *et al.*, "Fast LEDs for polymer optical fiber communication at 650nm," Proc. SPIE 6013, Optoelectronic Devices: Physics, Fabrication, and Application II, Oct. 2005.
- [4] J. W. Shi, *et al.*, "High-speed GaN-based green light-emitting diodes with partially n-doped active layers and current-confined apertures," IEEE Electron Device Lett., vol. 29, no. 2, pp. 158-160, Feb. 2009.
- [5] Y. F. Yin, *et al.*, "Far-field self-focusing and -defocusing radiation behaviors of the electroluminescent light sources due to negative refraction," Opt. Lett., vol. 38, pp. 184-186, 2013.
- [6] Y. F. Yin, *et al.*, "Correlation of angular light profiles of light-emitting diodes to spatial spontaneous emissions from photonic crystals," J. Appl. Phys., vol. 114, p. 143104, 2013.
- [7] Windisch, *et al.*, "Large-signal-modulation of high-efficiency light-emitting diodes for optical communication," IEEE J. Quant. Electron., vol. 36, no. 12, pp. 1445-1453, Dec. 2000

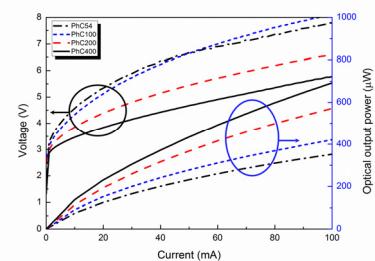


Fig. 2. Optical output and electrical property of different PhCLEDs.

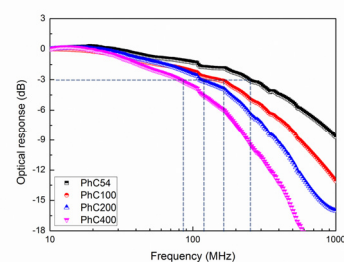


Fig. 3. Frequency response of different PhCLEDs at a 50 mA injection current.

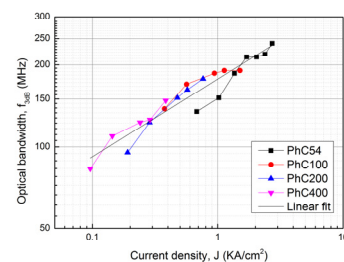


Fig. 4. The modulation bandwidth as a function of the injected current density of PhCLEDs.